

Josephson Vortex Lattice Melting in $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_8$

M. S. Fuhrer^a, K. Ino^b, K. Oka^b, Y. Nishihara^b and A. Zettl^a.

^aDepartment of Physics, University of California at Berkeley, and Materials Sciences Division, Lawrence Berkeley National Laboratory, Berkeley, CA 94720, USA.

^bElectrotechnical Laboratory, Tsukuba, Ibaraki 305, Japan

The Josephson vortex lattice state of the highly anisotropic high- T_c superconductor $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_8$ has been probed by measurements of the out-of-plane (c-axis) resistivity as a function of temperature, current density, magnetic field strength H , and magnetic field orientation angle θ . Anomalous dissipation is observed below a critical temperature identified as the melting transition of the Josephson vortex lattice. The critical T - H and T - θ phase boundaries are determined. The melting transition is interpreted as a Kosterlitz-Thouless depairing of interlayer vortex/anti-vortex pairs.

Crystals of $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_8$ (BSCCO-2212) were prepared using a traveling-solvent floating-zone (TSFZ) method described elsewhere¹. The crystals were cleaved to the desired dimensions, and electrical contacts were made using silver paint, fired at 650°C.

Samples were mounted on a cryostat which allowed *in situ* alignment with the magnetic field with an angular resolution of 0.013°. The cryostat was placed in the bore of a superconducting solenoid, allowing the measurement of the c-axis electrical resistivity of the samples as a function of temperature, current density, magnetic field strength H , and magnetic field orientation angle θ .

Figure 1 shows the c-axis resistivity of a BSCCO-2212 sample in a field of 18 Tesla aligned parallel to the ab-plane for two measuring current densities. The general field-induced broadening below the superconducting transition temperature (T_c) is consistent with previous studies². However, the high and low current data diverge below a temperature T_m , where the low current data show a sharp kink. Electric field as a function of current density ($E(J)$) curves taken above and below T_m show distinctly different

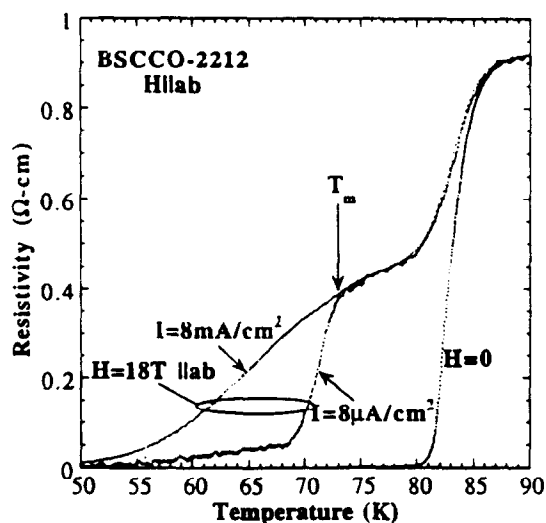


Figure 1. The c-axis resistivity of BSCCO-2212 at 18 Tesla $\parallel ab$ for two different measuring current densities. The zero field data are also shown.

behavior. For $T > T_m$, $E(J)$ is always linear, but for $T < T_m$, $E(J)$ is non-ohmic, displaying a well-defined critical current for the onset of dissipation with $E \sim (J - J_{crit})$ for $J > J_{crit}$ where J_{crit} is the critical current.

The kink in the resistivity seen in Fig. 1 is reminiscent of the kink in both the in-plane

and c-axis resistivities versus temperature observed in YBa₂Cu₃O₇ (YBCO) crystals³. It is noteworthy that in YBCO the dissipation kink is clearly observable at a current density of 4 A/cm², while in the configuration described here for BSCCO the kink is only apparent at much lower current densities, on the order of 10⁻⁴ A/cm². In the case of YBCO, the kink corresponds to melting of the Abrikosov vortex lattice or glass, with E(J) characteristics ohmic above and non-ohmic below the melting temperature.

We propose that T_m is the Josephson vortex lattice melting temperature in BSCCO-2212. T_m is therefore expected to have unique functional dependencies on the magnetic field magnitude and orientation which distinguish it from the melting transitions of the conventional ($H \parallel c$) vortex lattices in BSCCO-2212⁴. We have repeated the measurements in Fig. 1 for different H field strengths and alignments to map out the T - H and T - θ phase boundaries.

Figure 2 shows the critical temperature T_m needed to induce melting as a function of magnetic field angle θ with the ab -plane for a field of 7.5 Tesla. Anisotropic effective mass scaling theory, which predicts quite well the dependence of T_m on θ in YBCO, cannot fit the data for BSCCO (dashed line). T_m falls off too sharply with increasing field misalignment; phenomenologically, $H_m = H_m(\theta=0) - A(H \sin \theta)^2$.

The $H_m(T)$ line also does not follow the expected form for three-dimensional vortex melting. Notably, we find $H_m(T)$ tends to zero at a temperature several Kelvin below T_c .

We propose⁶ a model of a coupled Kosterlitz-Thouless and vortex lattice melting transition which can explain the H - θ and H - T phase diagrams. The Josephson vortex lattice is not expected to melt in the limit that the vortices are confined to lie in between superconducting planes⁵. However, segments of Josephson vortex are expected to be

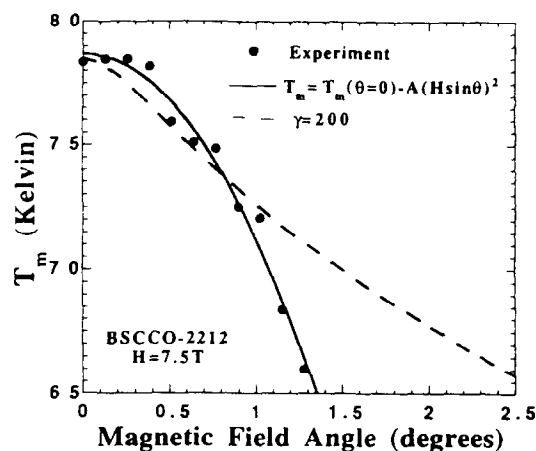


Figure 2. T - θ diagram for BSCCO-2212 with $H=7.5$ Tesla $\parallel ab$ -plane.

thermally excited across the superconducting planes at finite temperature via creation of a Kosterlitz-Thouless vortex-antivortex pair. Above the Kosterlitz-Thouless transition temperature this pair is free to separate, and the vortices may cross the planes freely, so the Josephson lattice may melt. Below T_{KT} , melting is forbidden.

T_{KT} should be quickly suppressed with application of a perpendicular magnetic field, as we observe. Also, since T_{KT} in zero field is a few Kelvin below T_c , we expect H_m to tend to zero a few Kelvin below T_c , as observed.

Supported by DOE contract DE-AC03-76F00098 and NSF grant DMR-9501156.

REFERENCES

1. D. H. Ha, et. al., Bulletin of the Electrochemical Laboratory **57**, 15 (1993)
2. G. Briceno, M. F. Crommie and A. Zettl, Physica C **204**, 389 (1993)
3. M. Charalambous, et. al., Phys. Rev. B **45**, 6249 (1992)
4. E. Zeldov, et. al., Nature **375**, 373 (1995); R. Cubitt, et. al., Nature **365**, 407 (1993)
5. K. B. Efetov, Sov. Phys. JETP **49**, 905 (1979)
6. M. S. Fuhrer, et. al., Solid State Comm. (to be published)